

ACEROS RÁPIDOS

Formatos disponibles

Productos largos*

Chapas

*) Presented data refer exclusively to long products. Please observe the detailed explanations at the end of the data sheet (pdf).

Descripción

BÖHLER S390 MICROCLEAN - "El decatleta"

Es un acero pulvimetalúrgico con muchas propiedades positivas de rendimiento. Si se trata de trépanos, machos de roscar, fresas, herramientas de brochado o aplicaciones de trabajo en frío, BÖHLER S390 MICROCLEAN siempre aporta el máximo rendimiento.

Método de obtención

Pulvimetalurgia

Propiedades

- > Dureza y Ductilidad : alto
- > Resistencia al desgaste : alto
- > Resistencia a la compresión : muy alta
- > Estabilidad de los bordes : muy alta
- > Afilabilidad : alto
- > Dureza en caliente (dureza roja) : muy alta

Aplicaciones

- > Carreras automovilísticas
- > Puntas de brocas
- > Compactación de polvo
- > Herramientas de corte especiales
- > Pill punching dies
- > Broches y escariadores
- > Corte fino / Troquelado / Estampado
- > Laminación
- > Brocas helicoidales y grifos
- > Conformado en frío / acuñado
- > Talladura de engranajes, herramientas de rasurado y perfiladoras
- > Cizallas / Cuchillas
- > Componentes de desgaste

Composición Química

C	Cr	Mo	V	W	Co
1,64	4,80	2,00	4,80	10,40	8,00

Características

	Resistencia a la compresión	Aptitud para el rectificado	Dureza en caliente	Tenacidad	Resistencia al desgaste	Retención del filo de la navaja
BÖHLER S390 MICROCLEAN®	★★★★	★★★	★★★★	★★★★	★★★★	★★★★
BÖHLER S290 MICROCLEAN®	★★★★★	★	★★★★	★★	★★★★★	★★★★
BÖHLER S393 MICROCLEAN®	★★★★	★★★	★★★★	★★★★	★★★★	★★★★
BÖHLER S590 MICROCLEAN®	★★★★	★★★	★★★★	★★★	★★★	★★★
BÖHLER S592 MICROCLEAN®	★★★★	★★★	★★★★	★★★	★★★	★★★
BÖHLER S690 MICROCLEAN®	★★★	★★★	★★	★★★★★	★★★	★★
BÖHLER S692 MICROCLEAN®	★★★	★★★	★★	★★★★★	★★★	★★
BÖHLER S790 MICROCLEAN®	★★★	★★★	★★	★★★★	★★	★★★
BÖHLER S792 MICROCLEAN®	★★★	★★★	★★	★★★★	★★	★★★
BÖHLER S793 MICROCLEAN®	★★★	★★★	★★★★	★★★	★★★	★★★

Estado de suministro

recocido

Dureza (HB)	máx. 320 drawn execution max. 320 HB
Resistencia a la tracción (MPa)	máx. 1.080

Endurecido y templado

Dureza (HRC)	64 a 68
--------------	---------

Tratamiento térmico

Recocido

Temperatura	770 a 840 °C	4 h controlled slow cooling in furnace (10 to 20°C/h / (50 to 68°F/h) to 740°C/2h (1364°F/2 h) cooling in furnace,
-------------	--------------	---

Alivio de tensiones

Temperatura	600 a 650 °C	Slow cooling in furnace. To relieve stresses set up by extensive machining or in tools of intricate shape. After through heating, hold in neutral atmosphere for 1 to 2 hours.
-------------	--------------	--

Temple y revenido


Temperatura	1.100 a 1.230 °C	Salt bath, vacuum Preheating: 1st stage ~ 500 °C (930 °F), 2nd stage ~ 850 °C (1560 °F), 3rd stage ~1050 °C (1920 °F) Austenitising: 1100 - 1230 °C (2012 °F - 2246 °F), holding time after complete heating 80 seconds, maximum 150 seconds, to avoid material damage due to overheating. Quenching: oil, warm bath (500 - 550 °C (930 °F - 1020 °F)), gas
Temperatura	550 a 570 °C	Slow heating to tempering temperature immediately after austenitising. Holding time in the furnace 1 hour per 20 mm material thickness (at least 1 hour) Slow cooling to room temperature between each tempering step 3 tempering cycles recommended Hardness see tempering chart

Continuous cooling CCT curves

Austenitising temperature: 1230°C
Haltedauer: 180 Sekunden

Austenitising temperature: 1230°C (2246°F)
Holding time: 180 seconds

Austenitising temperature: 1230°C (2246°F)
Holding time: 180 seconds

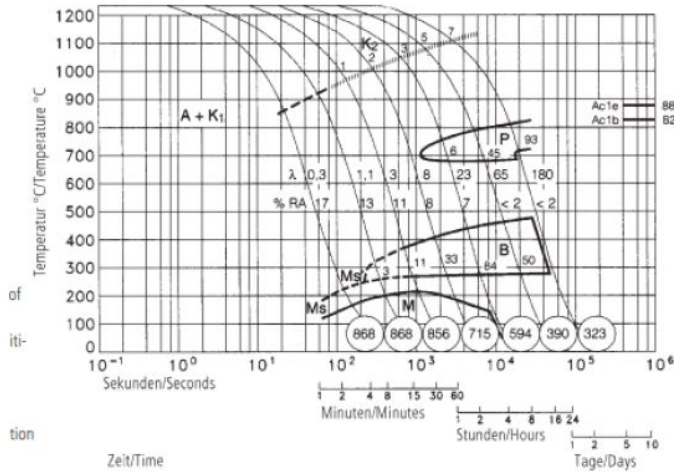


A....Austenite
B....Bainite
K....Carbide
P....Pearlite
M....Martensite
RA...Retained Austenite

Quantitative phase diagram

Austenitising temperature: 1230°C
Haltedauer: 180 Sekunden

Austenitising temperature: 1230°C (2246°F)
Holding time: 180 seconds

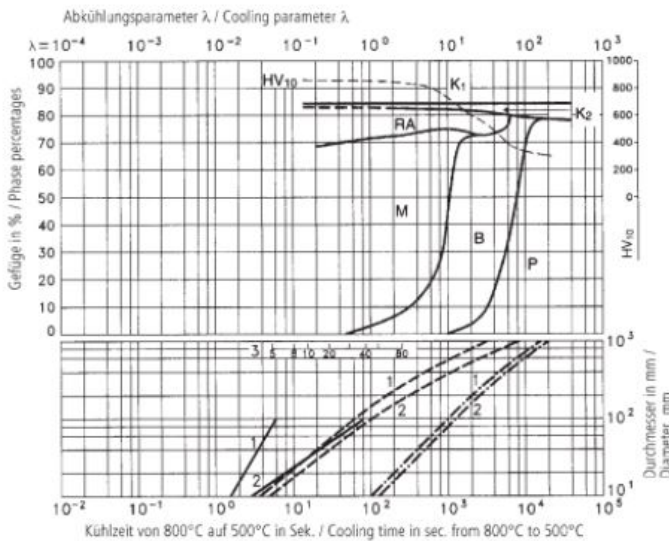


A....Austenite
B....Bainite
K....Carbide
P....Pearlite
M....Martensite
RA...Retained Austenite

1....Edge or Face
2....Core
3....Jominy test: distance from quenched end

— watercooling
- - oilcooling
- · - aircooling

Tempering Chart

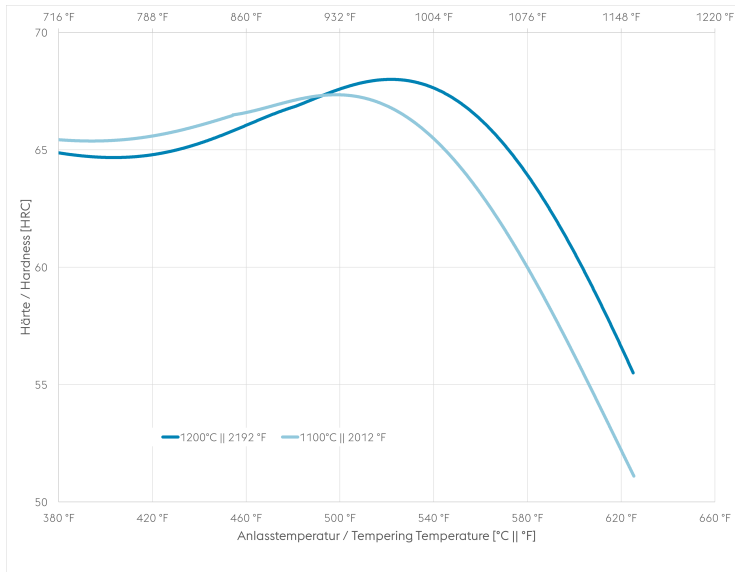

Holdingtime 3x2 hours

Specimensize: square 25mm

Austenitising in vacuum

Propiedades físicas

Temperatura (°C)	20
Densidad (kg/dm ³)	8,1
Conductividad térmica (W/(m.K))	17
Calor específico (kJ/kg K)	0,42
Resistencia eléctrica específica (Ohm.mm ² /m)	0,61
Módulo de elasticidad (10 ³ N/mm ²)	231

Expansión térmica

Temperatura (°C)	100	200	300	400	500	600	700
Expansión térmica (10 ⁻⁶ m/(m.K))	10	10,5	10,8	11,2	11,3	11,4	11,6

Long Products: For additional specifications and technical requirements, please contact our regional voestalpine BÖHLER sales companies.

Sheet & Plates: Product Variant may differ in terms of melting process, technical data, delivery, and surface condition as well as available product dimensions. Please contact voestalpine BÖHLER Bleche GmbH & Co KG.

The data contained in this brochure is merely for general information and therefore shall not be binding on the company. We may be bound only through a contract explicitly stipulating such data as binding. Measurement data are laboratory values and can deviate from practical analyses. The manufacture of our products does not involve the use of substances detrimental to health or to the ozone layer.